

# SYNTHESIS OF A POLYMERIC MATERIAL WITH SCRATCH MENDABILITY FROM POLYESTER-BASED BISMALIMIDE AND TRIS-FURAN

Tri Minh Phan<sup>1\*</sup>, Son Hong Thai<sup>2</sup>, Thanh Dac Nguyen<sup>3</sup>

<sup>1</sup> Polymer Research Center, Ho Chi Minh City University of Technology

<sup>2</sup> Faculty of material technology, Ho Chi Minh City University of Technology

\*Corresponding Author: [phanminhtri.minjin@gmail.com](mailto:phanminhtri.minjin@gmail.com)

(Received: July 30<sup>th</sup>, 2016; Accepted: August 31<sup>th</sup>, 2016)

## ABSTRACT

A new thermoset has been prepared from a bismaleimidic terminated polycaprolactone polyester and a tris-furan compound acting as a crosslinker via the Diels-Alder reaction between the furan and maleimide functionalities. Owing to the reversibility of the Diels-Alder chemistry and the increased mobility of the crosslinked polyester chains, this material had the ability to mend scratches under mild temperature conditions. The synthesized precursors and resulting crosslinked material were characterized using <sup>1</sup>H NMR, FT-IR, GPC, TGA and DSC methods. The scratch mendability of the material was investigated using optical microscopy.

**Keyword:** Scratch mendability, maleimide, furan, polycaprolactone polyester

## TÓM TẮT

Một loại polymer nhiệt rắn mới được tổng hợp từ polyester polycaprolactone mang nhóm bismaleimide ở cuối mạch và tris-furan, chúng liên kết với nhau nhờ phản ứng Diels-Alder giữa cặp nhóm chức furan và maleimide. Tris-furan đóng vai trò là một tác nhân nối mạng. Nhờ vào khả năng phản ứng thuận nghịch của nhóm Diels-Alder và tính linh động của mạch polyester nối mạng, vật liệu này có khả năng phục hồi vết trầy xước trong điều kiện nhiệt độ không cao. Các tiền chất tổng hợp và kết quả là polymer nối mạng được phân tích bằng các phương pháp <sup>1</sup>H-NMR, FT-IR, GPC, TGA và DSC. Quá trình phục hồi vết trầy xước của vật liệu được quan sát bằng kính hiển vi quang học.

**Từ khóa:** hồi phục vết nứt, maleimide, furan, polycaprolactone polyester

## INTRODUCTION

Nowadays, the application of polymeric coatings not only gives better processability but also provides a good protection due to their barrier properties. Nevertheless, these materials are easily damaged when continuously exposed to the external environment, such as mechanical attack, chemical abrasion, UV radiation, or a combination of these factors. Small defects are easily created in the coatings, but difficult or impossible to be detected and repaired. The presence of microcracks can adversely change the coating final properties, and can even develop further into damage which considerably shortens material lifetime.

In recent decades, various self-mending approaches have been developed rapidly, including microencapsulation, microvascular networks, supramolecular self-assembly and reversible chemistry. Among these approaches, intrinsic remendable polymeric systems, which contain reversible covalent

bonds, is a particularly attractive one. These polymer networks have repeatedly mending ability to repair the damage at the same position. The most prominent pathway is based on the Diels–Alder (DA) reaction. DA reactions occur between a diene and a dienophile at a temperature range from room temperature to 80 °C and can be reversed, via the retro-Diels–Alder (rDA) reaction at temperatures above 100 °C, yielding the original diene and the dienophile. This provides sufficient mobility to the network so as to flow locally and to repair surface microscratches. Thus, DA moieties allow the implementation of mending capabilities to polymeric networks without significantly compromising the original material properties [1].

On the other hand, polycaprolactone polyester (PCL) is a very attractive polymer due to its sustained biodegradability, low cost and availability. The cross-linking of homo-and copolymers of PCL often leads to

superior mechanical properties of these materials, such as high modulus and dimensional stability.

Therefore, in this paper, a polymer network was synthesized by the DA reaction between the maleimide moieties of a bismaleimidic polycaprolactone polyester and the furan groups of a tris-furan compound, and its scratch mendability was evaluated.

## EXPERIMENTAL

### Materials

Hexamethylene diisocyanate (HDI) (99%), 2-furfurylthiol (97%), triethylamine (99%) and zirconium(IV) acetylacetonate were purchased from Sigma-Aldrich. *n*-Heptane (99+%), chloroform (99+%), tetrahydrofuran (THF, 99.5+%) and toluene (99+%) were purchased from Fisher Chemicals. Hexamethylene diisocyanate isocyanurate trimer (Desmodur® N 3390 BA) was received from Bayer. 3-Maleimido-1-propanol was prepared according the previously reported procedure [2]. Poly(caprolactone) diol (PCL,  $M_n = 2100$  g/mol) was purchased from Acros).

### Synthesis of bismaleimidic polycaprolactone

HDI (2.0 mL, 12.4 mmol), freshly azeotropically dried PCL diol (13.15 g, 6.2 mmol) and zirconium(IV) acetylacetonate (121 mg, 1 mol% per OH group) were dissolved in 160 mL of dry chloroform under nitrogen atmosphere. The reaction was refluxed for 6 h. After the mixture was cooled down, 3-maleimido-1-propanol (1.93 g, 12.4 mmol) was added and the mixture was again refluxed. After 2 h, the reaction was kept at room temperature overnight under nitrogen atmosphere to assure that all –NCO groups were consumed. After the reaction, chloroform was removed. The product was re-dissolved in THF and precipitated into distilled water. The precipitate was washed with diethyl ether and dried under vacuum. Yield: 80%.

### Synthesis of tris-furan

42.513 g (155.6 mmol of NCO groups) of Desmodur N3390 BA was mixed with 20 mL (198.3 mmol) of 2-furfurylthiol in 110 mL of THF. Triethylamine (277  $\mu$ L) was then added and the reaction was stirred at room

temperature overnight. The product was precipitated into *n*-heptane, filtered and dried under vacuum to give a brown solid. Yield: 92%.

### Synthesis of the network from the bismaleimidic polycaprolactone and trisfuran

A mixture of bismaleimidic polycaprolactone and tris-furan in a 1:1 furan to maleimide equivalent ratio in tetrahydrofuran was cast in a glass petri disk at 40 °C for 48 h, followed by vacuum dried at 60 °C for 24 h.

### Characterization

<sup>1</sup>H NMR spectra were recorded in deuterated chloroform (CDCl<sub>3</sub>) with TMS as an internal reference, on a Bruker Avance 300 at 300 MHz. Transmission Fourier transform infrared (FT-IR) spectra, collected as the average of 128 scans with a resolution of 4 cm<sup>-1</sup>, were recorded from KBr disk on the FT-IR Bruker Tensor 27. Attenuated total reflectance (ATR) FT-IR spectra were collected as the average of 128 scans with a resolution of 4 cm<sup>-1</sup> on a FT-IR Tensor 27 spectrometer equipped with a Pike MIRacle ATR accessory with a diamond/ZnSe element. Size exclusion chromatography (SEC) measurements were performed on a Polymer PL-GPC 50 gel permeation chromatograph system equipped with an RI detector, with chloroform as the eluent at a flow rate of 1.0 mL/min. Molecular weight and molecular weight distribution were calculated with reference to polyethylene glycol standards. Differential scanning calorimetry (DSC) measurements were carried out with a DSC Q20 V24.4 Build 116 calorimeter under nitrogen flow, at a heating rate of 10 °C/min, from -40 to 170 °C. Thermogravimetric analysis (TGA) measurements were performed under nitrogen flow using a NETZSCH STA 409 PC Instruments with a heating rate of 10 °C/min from ambient temperature to 900 °C. Optical microscopic images were recorded on an Olympus GX51F microscope.

## RESULT AND DISCUSSION

### Synthesis of bismaleimidic polycaprolactone

Polycaprolactone diol ( $M_n = 2100$  g/mol; 1 equivalent) was reacted with hexamethylene

diisocyanate (2 equivalents) via the OH-NCO reaction, catalyzed by zirconium(IV) acetylacetonate, to give diisocyanate terminated polycaprolactone. This intermediate product was further reacted with 2 equivalents of 3-maleimido-1-propanol by the OH-NCO reaction which was catalyzed by zirconium(IV) acetylacetonate. The unreacted 3-maleimido-1-propanol was removed by precipitation of the resulting polymer in water (3-maleimido-1-propanol is soluble in water). As a result, polycaprolactone containing two maleimide moieties at the polymer chain ends was obtained. The  $^1\text{H}$  NMR spectrum of this maleimide-terminated polycaprolactone is shown in Figure 1, with all the peaks assigned to its chemical structure. The presence of the urethane (OCONH) peak and at 4.7 ppm and maleimide peak at 6.73 ppm indicates the successful occurrence of the OH-NCO reactions and incorporation of maleimide moieties. The FT-IR spectrum of the product in Figure 2 shows the complete disappearance of the NCO group at  $2270\text{ cm}^{-1}$  and the presence of typical maleimide absorption bands at  $837$  and  $697\text{ cm}^{-1}$  [3], confirming that the maleimide groups were attached to the polycaprolactone chains. The molecular weight and molecular weight distribution of this product as determined by SEC were  $3800\text{ g/mol}$  and  $1.4$ , respectively.

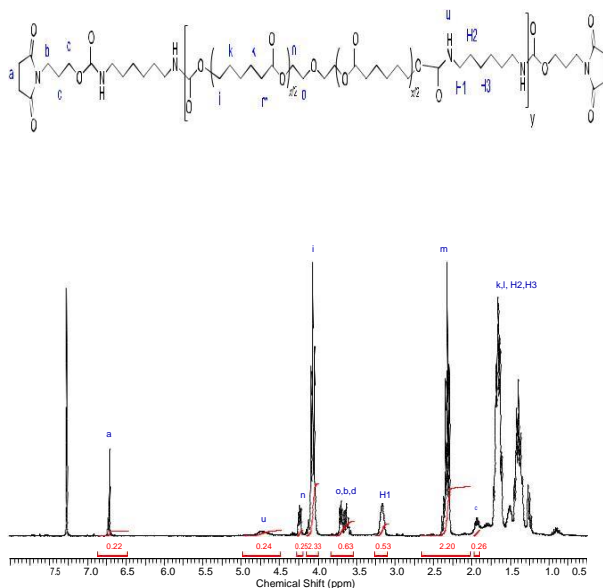


Figure 1.  $^1\text{H}$  NMR spectrum of bismaleimidic polycaprolactone.

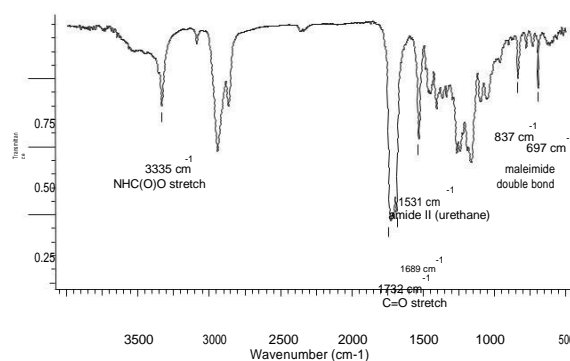


Figure 2. Transmission FT-IR spectrum of bismaleimidic polycaprolactone.

### Synthesis of tris-furan

Tris-furan was synthesized by the thiol-isocyanate reaction of 2-furfurylthiol and the hexamethylene diisocyanate isocyanurate trimer compound bearing three isocyanate functionalities. As a result, the product containing three furan moieties was obtained. As shown in the  $^1\text{H}$  NMR spectrum in Figure 3 of this product, all the peaks characteristic of its chemical structure can be assigned. The appearance of the furan peak at  $6.21$ ,  $6.29$  and  $7.32$  ppm and the thiourethane peak at  $5.54$  ppm indicates the successful incorporation of the furan groups into the structure of the isocyanurate trimer via the thiourethane formation reaction. This result was confirmed by transmission FT-IR analysis. As shown in Figure 4, the band corresponding to the NCO group at  $2270\text{ cm}^{-1}$  disappears completely and the IR absorption band at  $1013\text{ cm}^{-1}$  was assigned to the signals of the furan functionality [8].

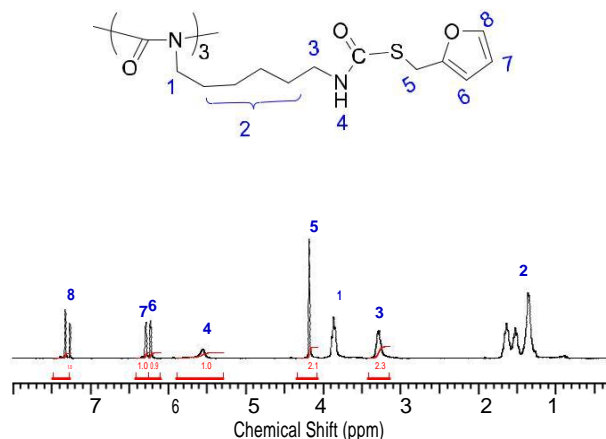


Figure 3.  $^1\text{H}$  NMR spectrum of tris-furan.




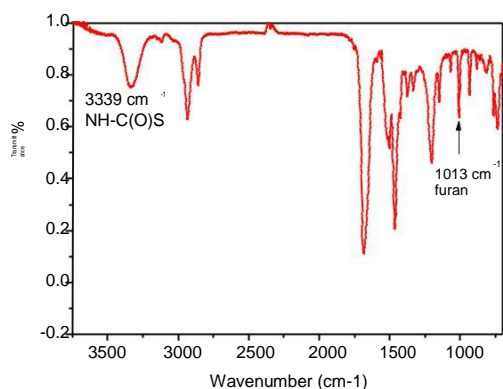


Figure 4. Transmission FT-IR spectrum of tris-furan.

### Characterization of the network formed from bismaleimide polycaprolactone and tris-furan

The network was created by the crosslinking DA reaction between the furan and maleimide moieties (Scheme 1).



Scheme 1. Diels-Alder (DA) reaction between maleimide and furan groups.

The occurrence of the DA reaction was confirmed by the FT-IR result. As shown in the ATR FT-IR spectrum of the material in Figure 5, the almost disappearance of the maleimide bands at 828 and 696  $\text{cm}^{-1}$  as well as the furan bands at 1011  $\text{cm}^{-1}$  suggests the nearly complete reaction between furan and maleimide to form DA-adduct bonds.

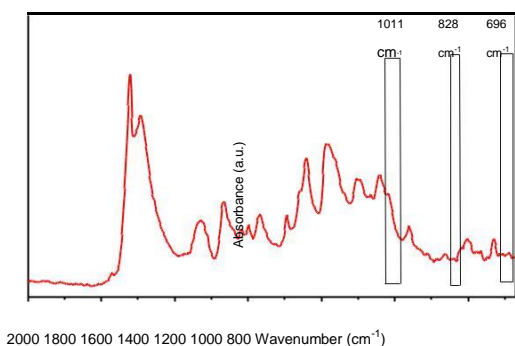


Figure 5. ATR FT-IR spectrum of the crosslinked network.

The TGA analysis result of the cast crosslinked film showed that the polymer network was stable up to above 200  $^{\circ}\text{C}$  (Figure 6a), while the thermal reversibility of the DA crosslink bonds was attested by DSC analysis. The first DSC heating scan (Figure 6b) showed a large endothermic region from 20 to 60  $^{\circ}\text{C}$  attributed to the melting of the

crystallized PCL segments, and another endothermic peak starting at around 90-100  $^{\circ}\text{C}$  attributed to the rDA reaction, indicating the cleaving of cross-linked bonds [8]. The samples were subsequently quenched in liquid nitrogen to avoid the re-formation of DA bonds upon cooling. The second scan included a PCL crystallization exotherm at -15  $^{\circ}\text{C}$ , followed by a PCL melting peak at 45  $^{\circ}\text{C}$ . An exothermic peak from approximately 60 to 120  $^{\circ}\text{C}$  was observed and was followed by an endothermic peak at above 125  $^{\circ}\text{C}$ . These two transitions were attributed to the cross-linking and cleaving transitions via the DA and rDA reactions, respectively [9]. These transition temperatures were in the same range as previously reported for DA cross-linked materials [4,5]. The appearance of these two DA and rDA transitions in the second scan suggested that the quenched samples contained disconnected furan and maleimide moieties, which re-connected when the molecules gained sufficient mobility at increased temperatures. Compared to the first scan, the smaller area of the rDA endotherm in the second scan represents the lower relative content of DA netpoints in the material due to the shorter reaction time.

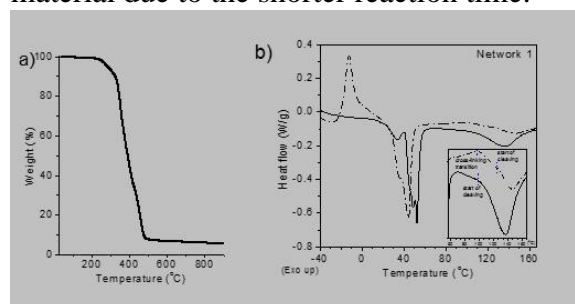


Figure 6. TGA (a) and DSC (b) thermograms (solid line: first heating scan; dash-dotted line: second heating scan; inset: zoom-in of the transitions at 60-170  $^{\circ}\text{C}$ ) of the crosslinked network.

### Assessment of the scratch mendability

To assess the scratch mendability of the obtained network, a scratch was made in the coating using a razor blade. Afterward, the scratch was repaired by heating the scratched coating sample at 60  $^{\circ}\text{C}$ . At this temperature, the polycaprolactone segments melt, leading to an activation of the chain entropy. Thus, the material gain sufficient local mobility, so that the reversible reaction between the furan



and maleimide moieties at the scratch interface could occur. On the other hand, the reformation of the broken DA bonds is favored at 60 °C [5]. As seen in the optical microscopic images in Figure 7, the scratch was considerably reduced by heating the sample at 60 °C for 5 min. After 21 h at 60 °C, the scratch almost healed, with only a scar due to interface mismatch.



Figure 7. Optical micrographs of scratches of the network sample before ( $t=0$ ) and after healing at 60 °C for 5 min and 21h.

## CONCLUSIONS

A polymer network with scratch mendability at mild temperature conditions was

successfully prepared via the Diels-Alder reaction between a bismaleimidic polycaprolactone and a tris-furan compound. Remendability was achieved by combining the occurrence of two processes at 60 °C: an increase in polymer chain mobility, triggered by the melting of the crystallized polycaprolactone phase, brought the free furan and maleimide moieties together, after which a progressive Diels-Alder reaction could reform the covalent bonds on a longer time scale.

**Acknowledgments:** This research was supported by the Department of Science and Technology (DOST) – Ho Chi Minh City, under the program “Incubator for Young Science and Technology Creators” (2014), contract number: 279/2014/HĐ-SKHCHN.

## REFERENCES

- TASDELEN, M. A., POLYM. CHEM., 2011, 2, 2133-2145.  
 NARITA, M., TERAMOTO, T., OKAWARA, M., BULL. CHEM. SOC. JPN., 1971, 44, 1084-1089.  
 RIVERO, G., NGUYEN, L.-T. T., HILLEWAERE, X. K. D., DU PREZ, F. E., MACROMOLECULES, 2014, 47, 2010-2018.  
 HEO, Y., SODANO, H. A., ADV. FUNCT. MATER., 2014, 24, 5261-5268.  
 CHEN, X., DAM, M. A., ONO, K., MAL, A., SHEN, H., NUTT, S. R., SHERAN, K., WUDL, F., SCIENCE, 2002, 295, 1698-1702.

